



encoremals



Continuous Cast Iron Bar Stock

WESTERN CANADA'S SOURCE FOR SPECIALTY METALS & PROCESSING

VANCOUVER / PRINCE GEORGE / CALGARY / EDMONTON / WINNIPEG

encoremals.com



Versa-Bar® grades compared to other standards (*)


Versa-Bar® Grade	ASTM		DIN		SAE	UNI
	A 48	A 159	1691	EN 1561	J 431	5007
FC 100	20	G 1800	GG 10	EN-GJL-100	G 1800	G 10
FC 200	30	G 2500	GG 20	EN-GJL-200	G 2500	G 20
FC 250	35	G 3000	GG 25	EN-GJL-250	G 3000	G 25
FC 300	40	G 3500	GG 30	EN-GJL-300	G 3500	G 35

Versa-Bar® Grade	ASTM	DIN	SAE	UNI
	A 536	1693	J 434	4544
FE 40015	60-40-18	GGG 40	D-4018	GS 370-17
FE 45012	65-45-12	-	D-4512	GS 400-12
FE 50007	-	GGG 50	-	GS 500-7
FE 55006	80-55-06	-	D-5506	-
FE 60003	-	GGG 60	-	GS 600-2
FE 70002	100-70-03	GGG 70	D-7003	GS 700-2

(*) The information provided is only intended to be a general summary. It is important to say that materials are not equal, but similar.




Continuous Cast Process

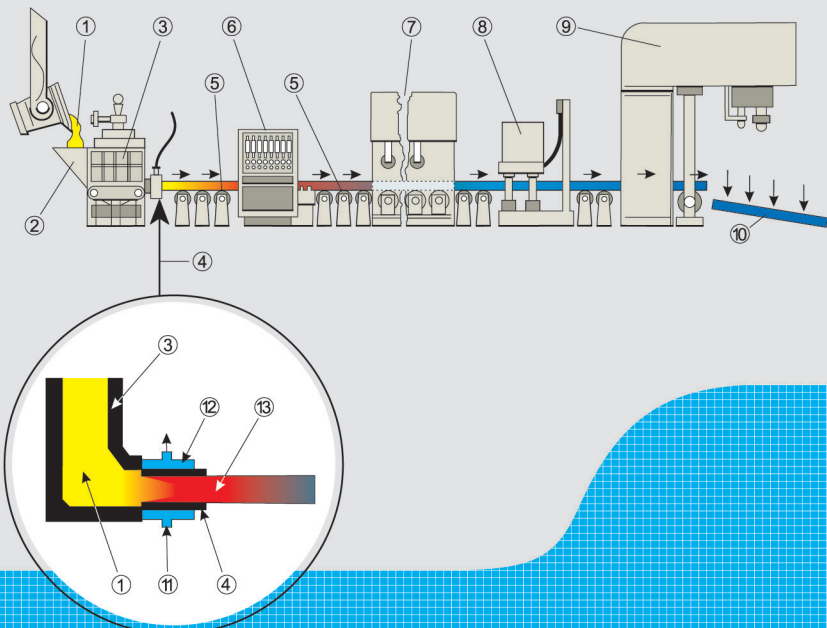

- 1 - Molten Metal
- 2 - Filling Spout
- 3 - Feeding Furnace
- 4 - Water Cooled Graphite Die
- 5 - Roller Supports
- 6 - Control Panel
- 7 - Drawing Unit
- 8 - Cut-off machine
- 9 - Break-off Unit
- 10 - Stock Size
- 11 - Water inlet and outlet
- 12 - Water Cooling Jacket
- 13 - Cast Bar - VERSA-BAR®

August 2015 NovaPEB

Available from:

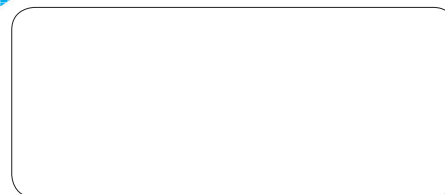

VANCOUVER

7470 Vantage Way
Tilbury Industrial Park
Delta, British Columbia
V4G 1H1
Phone: 604 940 0439
Toll Free: 800 940 0439
Fax: 604 940 0462

EDMONTON

9810-39th Avenue
Edmonton, Alberta
T6E 0A1
Phone: 780 436 6660
Toll Free: 800 661 5621
Fax: 780 435 5976

CALGARY

7805-51st Street S.E.
Calgary, Alberta
T2C 2Z3
Phone: 403 236 1418
Toll Free: 800 661 4140
Fax: 403 236 0844

WINNIPEG

333 DeBaets Street
Winnipeg, Manitoba
R2J 3V6
Phone: 204 663 1450
Toll Free: 800 665 9835
Fax: 204 663 1456



Sizes and Shapes

Inches

Shape	Nominal Diameter	Increments	Weight Calculation (lb/in)
Round	0.625 – 4.000	0.125	$d^2 \times 0.20430$
	4.250 – 11.000	0.250	
	11.500 – 15.000	0.500	
	16.000 – 22.875	1.000	
Square	1.125 – 4.000	0.250	$w^2 \times 0.26011$
	4.250 – 9.000	0.500	
	9.500 – 18.500	1.000	
Rectangle	0.750 – 16.000 (height)	-	$w \times h \times 0.26011$
	1.125 – 24.000 (width)	-	

Standard length = 72" (-1" / + 2")

Special sizes and shapes quoted under request.

Millimeters

Shape	Nominal Diameter	Increments	Weight Calculation (kg/m)
Round	30 – 150	5	$d^2 \times 0,005655$
	160 – 430	10	
	450 – 600	20	
Square	30 – 100	5	$w^2 \times 0,0072$
	110 – 300	10	
	330 – 470	30	
Rectangle	20 – 410 (height)	-	$w \times h \times 0.0072$
	30 – 610 (width)	-	

Standard length = 2.000mm and 3000mm (-0 / + 100 mm)

Special sizes and shapes quoted under request.

Typical Applications

Class 35 GJL 250	Its main characteristic is its excellent machinability, allowing high cutting speed and reduction of premature tooling wear. It is suitable for applications that require medium mechanical properties as bushings, pulleys, rings, sheaves, pattern plates, flanges, plugs, structures for machines, bearings, couplings.
Class 40 GJL 300	It presents good surface finish and leaking strength. It is suitable in applications subjected to wear such as pistons, hydraulic valves, dies, pattern plates, couplings, spacers.
60-40-18 GJS 400-15 65-45-12	The main characteristics of these materials are good machinability, excellent surface finish and very good leakage strength. They also show ultimate tensile strength and yield strength similar to steel SAE 1020/1030. They are suitable for machine components subjected to impact and resistant to cracking. They are also an excellent choice for hydraulic components that operate in high pressure such as manifolds, pistons, guides, cylinder heads, injector jackets, hydraulic pumps and dies.
GJS 500-7 80-55-06 GJS 600-3 100-70-03 GJS 700-2	These materials offer good hardenability and high mechanical properties. The ultimate tensile strength and yield strength of these materials are similar of that found on steel SAE 1040/1045. They are an excellent choice for machine components that require wear resistance and surface heat treatment response. Some examples are gears, axles, tie rod nuts, chuck bodies, piston glands, spindle housings, camshafts, valve seats, etc.

Material Properties

Properties	Diam/Height (inches) (millimeters)	Gray Iron		Ductile Iron					
		Class 35 GJL 250	Class 40 GJL 300	60-40-18 GJS 400-15	65-45-12	GJS 500-7	80-55-06	GJS 600-3	100-70-03 GJS 700-2
Tensile Strength (MPa)	≤ 3.000 ≤ 80	210	250	400	450	500	550	600	700
	$>3.000 \leq 6.250$ $>80 \leq 160$	190	220	390	440	480	540	590	690
	$>6.250 \leq 11.875$ $>160 \leq 300$	170	210	380	430	470	530	580	680
	$>11.875 \leq 23.625$ $>300 \leq 600$	160	190	370	420	450	520	550	660
Yield Strength (MPa)	≤ 3.000 ≤ 80	*	*	250	290	320	340	370	420
	$>3.000 \leq 6.250$ $>80 \leq 160$	*	*	250	280	310	330	360	400
	$>6.250 \leq 11.875$ $>160 \leq 300$	*	*	240	270	300	320	350	390
	$>11.875 \leq 23.625$ $>300 \leq 600$	*	*	240	260	290	310	340	380
Elongation (%)	≤ 3.000 ≤ 80	*	*	15	12	7	6	3	2
	$>3.000 \leq 6.250$ $>80 \leq 160$	*	*	14	12	7	6	2	2
	$>6.250 \leq 11.875$ $>160 \leq 300$	*	*	11	10	5	5	1	1
	$>11.875 \leq 23.625$ $>300 \leq 600$	*	*	11	10	5	5	1	1
Hardness (HB)		170 - 240	200 - 290	131 - 207	131 - 217	170 - 240	187 - 269	200 - 290	235 - 310
Shear Strength (MPa)		1,5 x Tensile Strength (TS)		0,9 x Tensile Strength (TS)					
Torsion Strength (MPa)		1,5 x Tensile Strength (TS)		0,9 x Tensile Strength (TS)					
Fatigue Strength (MPa)		0,4 x Tensile Strength (TS)		0,5 x TS	0,45 x TS	0,4 x TS	0,4 x TS	0,4 x TS	0,4 x TS
Compressive Strength (MPa)		TS (140 to 175 MPa) x 4,02		1,7 x TS	1,65 x TS	1,6 x TS	1,5 x TS	1,45 x TS	1,4 x TS
		TS (176 to 210 MPa) x 3,68							
		TS (211 to 245 MPa) x 3,61							
		TS (246 to 280 MPa) x 3,39							
Impact Strength - V notched (j)		*	*	13 - 15	5 - 10	5 - 10	2 - 5	2 - 5	1 - 4
Thermal Conductivity at 300°C - (W/k.m)		46 - 49	44 - 47	36 - 37	36 - 37	35 - 36	33 - 34	32 - 33	31
Linear Expansion Coefficient - 20°C to 400°C (microns/m.k)		10 - 12,5		10 - 12,5					
Poisson's ratio		0,26		0,275					
Max. Magnetic Permeability (microhoms/m)		310 - 380		2140	2140	1600	1100	870	500
Hysteresis los (B= 1T) - (J/m³)		2500 a 3000		600	600	1300	1600	2200	2700
Heat Treat Responde (HRC)		45 - 55		45 - 55					